

Generation of Value Added Product by Beneficiation of Barite Waste

P. Bhattacharyya¹, R. Singh²

¹Padmashree K. Acharya College of Engineering, Bargarh, Odisha, India

²National Metallurgical Laboratory, Jamshedpur - 831007, Jharkhand, India

Keyword: Barite waste; Environment; Value added product.

Abstract

One of the largest indigenous manufacturing plants of barium chemicals is located at Cuddapah in Andhra Pradesh. During production of barium carbonate, two types of rejects (flue ash and sludge) have been generated and accumulated for the last few decades at Cuddapah plant. Earlier, briquetting of charge was suggested to restrict physical losses of material as flue ash. Afterwards, to generate product, having >90% barium sulphate which could be reused, studies have been carried out with currently produced rejects. Detail investigations suggested separate treatment of sludge because the flue ash sample was found to be suitable as feed to the reduction circuit. Both gravity and flotation processes were found to generate product meeting specifications. It was also found that more than 55% of the combined rejects currently generated at Cuddapah plant could be used again for the production of barium carbonate. In the process, recovery of barite value could be more than 65%.

1. Introduction

The treatment of mineral wastes and its utilisation, for the conservation of mineral wealth and protection of environment, have become very important now a day. Wastes generated by the mining, mineral processing and metallurgical industries should be disposed of with a minimum environmental degradation and at acceptable cost. Some of the metallic and mineral constituents of these wastes are valuable, and their recovery can lead to substantial conservation of resources. Present study pertains to recovery of values from wastes (flue ash and sludge) generated during recent operation at Cuddapah barite plant (Figure-1). The problem of environmental pollution caused by the rejects generated during the processing of barite could be tackled in two ways - by controlling generation of

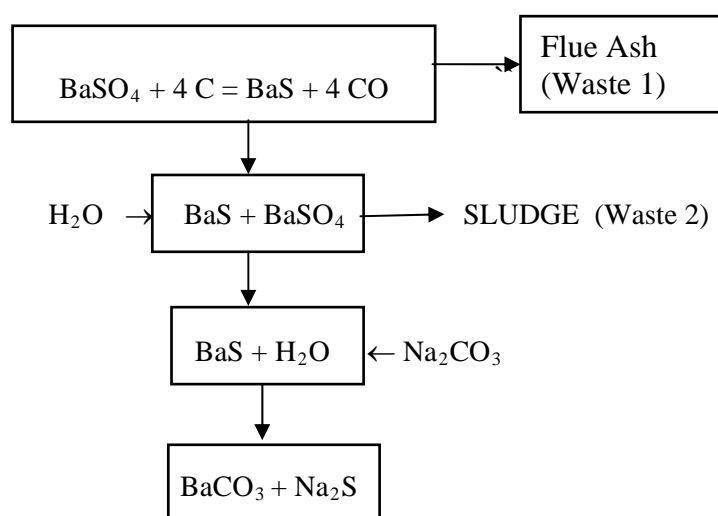


Fig 1. Scheme adopted for processing of barite

rejects itself and by development of process to recover values from the rejects, before discard, for reuse. During production of barium carbonate, two types of rejects (flue ash and sludge) have been generated and accumulated for the last few decades. It is anticipated that the total accumulated waste would be of the order of 50,000 T causing environmental pollution to the surroundings. While the reduction process of barium sulphate (barite) to barium sulphide generates flue ash, leaching of barium sulphide using hot water generates sludge as reject. The plant uses fine size barite (<250 μm) and coarser carbon particles. The types of carbons used for reduction are lecofines and LTC sludge. It has been found that composite waste (flue ash and sludge) contained nearly 75% barium sulphate in it and the sludge contained around 69% barium sulphate.

Recovery of high grade barite from waste pond materials, tailings ponds and bypassed mining wastes, contaminated drilling mud, mill wastes etc. through physical / chemical route have been reported earlier [1-6]. Flotation of fine-size barite from gravity separation tailing, high-intensity magnetic separation of ferrous tailing from barite flotation and dual centrifuge system with flocculation for mud treatment have also been reported for improved barite recovery[7-9]. Studies were carried out to utilise different wastes generated during barium carbonate manufacture [10]. All of the above studies were carried out in abroad. Recently generation of barite waste (flue ash) was reduced by using briquettes in black ash process during manufacture of BaCO_3 at Cuddapah plant, Andhra Pradesh, India [11]. Briquetting of charge was found to restrict physical losses of material as flue ash - which was generated due to heavy draft in the furnace

resulting in blowing up of fine and lighter particles of the charge continuously from the rotary furnace as flue ash. In the plant practice, using the briquetted charge an improvement of overall yield of more than 25% in comparison to the normal powder charge was reported. Studies with multi-gravity separator (MGS) to recover high grade barite from composite wastes (prepared from flue ash and sludge) and also separately from sludge have been carried out [12-13]. While the desired grade could be achieved, recovery was not appreciable. Use of MGS for concentration of complex lead zinc ore in preference to conventional froth flotation has also been reported [14].

In the present study, experiments were carried out using different gravity separators with sludge sample. Flotation studies were also carried out. Results have been presented to show the amenability of the processes to produce usable product from the wastes.

2. Sample

Two types of wastes (flue ash and sludge) were received separately at NML for the development of process flow sheet to recover barite value. Flue ash and sludge produced during recent operation (Photos 1-2) were sent for study. Accumulated flue ash and sludge heaps are shown in Photos 3-4. Size and chemical analysis of the Flue ash, sludge and composite sample are given in Tables (1-2).



Fig 1: Currently produced flue ash



Fig 2: Currently produced sludge



Fig 3: Accumulated flue ash heap



Fig 4: Accumulated sludge surrounding plant

Table 1: Size Analysis of as-received Flue ash and Sludge Samples

Size in mesh	SAMPLE	
	Flue ash Wt(%)	Sludge Wt(%)
+ 10	-	5.68
- 10 + 14	-	9.02
- 14 + 20	-	8.92
- 20 + 28	-	12.02
- 28 + 35	-	7.39
- 35 + 48	-	5.70
- 48 + 65	1.47	7.34
- 65 + 100	1.21	4.68
- 100 + 150	2.69	9.05
- 150 + 200	4.48	6.62
- 200	90.15	23.58
Head (Calc.)	100.00	100.00

Table 2: Chemical analysis for different size fractions of flue ash & sludge

Size in mesh	ASSAY(%)	
	Flue ash BaSO ₄	Sludge BaSO ₄
+ 10	-	45.62
- 10 + 14	-	49.80
- 14 + 20	-	49.93
- 20 + 28	-	52.82
- 28 + 35	-	55.49
- 35 + 48	-	58.53
- 48 + 65	86.16	64.58
- 65 + 100	88.16	76.87
- 100 + 150	87.08	80.86
- 150 + 200	86.24	79.62
- 200	91.58	96.44
Head (Calc.)	91.10	68.99

3. Experimental Procedure

It was observed, from size and chemical analysis, that more barite values were contained at finer sizes. Mineralogical studies also indicated a trend of enrichment of barite in finer sizes. So, it was decided to go for size reduction in order to achieve proper liberation of values before applying gravity methods and flotation for barite recovery. Initially, composite sample was prepared from as-received flue ash and sludge samples, at the proportion suggested by the sponsor, for study. But detail investigations with as received samples suggested separate treatment of sludge because the flue ash sample was found to be suitable as feed to the reduction circuit. Accordingly, experiments were carried out with sludge sample. Experiments results using different gravity separators and flotation process are given below and finally presented in Table 3.

3.1 Studies with MGS

Efficacy of MGS has been investigated using “design of experiment” technique which involves selection of strategy to obtain an adequate model with a minimum of experimentation. In the present study, experiments were performed considering four variables (feed pulp density, slope, wash water rate and rotational speed) at two levels using -200 mesh feed and it was possible to achieve the required grade of BaSO_4 (>90%) with recovery of BaSO_4 around 53%.

3.2 Studies with Hydrocyclone

As seen in Table 2, -65 mesh fraction of sludge sample contained considerable barite value. Accordingly, -65 mesh fraction was screened out from sludge sample and ground to 86% -200 mesh and subjected to hydrocyclone. Design and operating parameters were optimised to generate product containing more than 90% BaSO_4 in it. It was observed that at lower feed pulp density, product containing >95% BaSO_4 could be achieved with recovery of BaSO_4 around 54%. But to improve recovery, feed pulp density was increased as high as 30% (which reduces consumption of water to a great extent) - still it was possible to achieve product containing nearly 92% BaSO_4 with recovery of BaSO_4 more than 86% of feed. It was also observed that recovery could be further improved by second stage of hydrocycloning with the underflow product.

3.3 Flotation Studies

For this purpose, the -10 # sample was wet ground (-200 #) in laboratory rod mill and was floated to produce rougher concentrate which was subjected to two cleaning flotation with oleic acid emulsion as collector for each cleaning. The Cleaner Concentrate I assayed 89.1 % BaSO_4 with 77.5% distribution. Second cleaning further improved the grade over 92 % BaSO_4 . In order to

study the effects of regrinding on selectivity of separation another cleaning flotation experiment was also carried out. In this case the Cleaner Concentrate I analysed 90.7% BaSO_4 with 74% recovery. The second cleaning showed an improvement in grade to 94% BaSO_4 . The reagent requirement was found to be less in comparison to the cleaning flotation without regrinding. This might be due to dilution of reagent during the process of regrinding and also due to the generation of new mineral surfaces on grinding. Again, recycling of the middlings in a continuous circuit is expected to improve recovery. The losses in the primary tailings was 10-14%.

Table 3: Results of different processes

Process	Sample	Yield (%)	Assay BaSO ₄ (%)	Recovery BaSO ₄ (%)
Grinding + MGS	Sludge	48.9*	91.6*	53.1*
Grinding + Flotation	Sludge	63.2*	91.8*	68.4*
Screening + Grinding + Hydrocyclone	Sludge	60.3*	91.5*	63.1*

*Including Flue ash

4. Conclusions

From the above study it can be concluded that:

- Flue ash and sludge samples should be treated separately for best possible recovery of barite values.
- More than 55% of the combined wastes currently generated at Cuddapah plant can be recycled for the production of BaCO₃. In the process, recovery of barite value could be more than 65 %.
- In the present study, process has been developed at the bench scale level for currently produced wastes only and should be validated through pilot plant trials before implementation.

5. Acknowledgement

The authors are thankful to Dr. S. Srikant, Director, NML and Management of PKACE, Bargarh, Odisha for their constant encouragement and kind permission to present this paper. Thanks are also due to other colleagues who contributed to generate the data discussed in this paper.

6. References

- [1]. Sullivan G.V. and Lamont W.E., Recovery of barite from tailings ponds and bypassed mining waste, *Min. Eng.*, (33-II), 1981, pp. 1632.
- [2]. Lamont W.E., Davis E.G. and Sullivan G.V., 1980, In: Proc. Miner. Waste.Util. Symp., 7th, Retreatment of tailings to recover barite, P. 26.
- [3]. Sobieraj S. and Slaczka A., Recovery of barite from waste slimes by the flocculation-flotation method, *Fizykochem. Pobl. Mineralurgi*, (14), 1982, pp.29.
- [4]. Lamont W.E. and Sullivan G.V., Recovery of ultrafine barite from mill wastes, *Rep. Invest.—U.S., Bur. Mines*, RI 8668, 1982, pp.25.

- [5]. Lamont W.E. and Sullivan G.V., Recovery of high grade barite from waste pond materials, *Ibid*, RI 8673 , pp. 16.
- [6]. Fatieva R . Sh., Marnedov I.A., Abduragimova L. A. and Mirza A.S., Study of the possible utilization of drilling wastes, *Azerb. Neft. Khoz.*, (II), 1982, pp . 31.
- [7]. Lenzo R. and Sarquis P.E. , Flotation of fine-size barite from gravity separation tailings, *Miner. Metall. Process*, (12-2), 1995, pp.118.
- [8]. Neidhardt D., Duel centrifuge system with flocculation improves barite recovery, *Oil Gas J.*, 1993, (91-II), pp 63.
- [9]. Klisuranov G., Ivanov I. and Burzov G., High-intensity magnetic separation of ferrous tailings from barite flotation of kremikortsii ore, *God. Vissh. Minno – Geol. Inst.*, Sofiya, 30(4), 1984, pp 237.
- [10]. Jiang Y. and Hao X., Utilisation of the wastes from barium carbonate manufacture, *Huanjing Baohu* , (8) , 1993, pp. 90.
- [11]. Gokarn A.N., D. D. Ravetkar D.D. and S.S. Kulkarni S.S., 1997, In : Processing of Fines (1), Waste reduction at the source and waste recycle through briquetting of the reduction charge in the black-ash process , NML Publication , Jamshedpur, India, P. 266.
- [12]. Bhattacharyya P., Sarkhel B.R. and Maulik S.C. , Efficacy of multi-gravity separator in recovery of values from waste using experimental design, *NML Tech Jour.* , (40- 4), 1998, pp. 109.
- [13]. Bhattacharyya P., Sil S.K., Saha P. and Maulik S.C., 2000, In: Processing of Fines (2), Recovery of values from barite sludge using multi-gravity separator, NML Publication , Jamshedpur, India, P. 362.
- [14]. Gaur R.K., Sharma N.K. and Sharma V.R., 1997, In: Processing of Fines (1), Reducing the entrainment of concomitant ultra-fines by MGS in lead concentrate of Rajpura-Dariba concentrator, NML Publication , Jamshedpur , India, P. 64.
-